arXiv:1302.4905v1 [physics.ins-det] 20 Feb 2013

$CdWO_4$ crystal scintillators from enriched isotopes for double beta decay experiments

D.V. Poda[a,*], A.S. Barabash[b], P. Belli[c], R. Bernabei[c,d], R.S. Boiko[a], V.B. Brudanin[e], F. Cappella[f,g], V. Caracciolo[h], S. Castellano[h], R. Cerulli[h], D.M. Chernyak[a], F.A. Danevich[a], S. d'Angelo[c,d], V.Ya. Degoda[i], M.L. Di Vacri[h], A.E. Dossovitskiy[j], E.N. Galashov[k], A. Incicchitti[f,g], V.V. Kobychev[a], S.I. Konovalov[b], G.P. Kovtun[l], M. Laubenstein[h], A.L. Mikhlin[j], V.M. Mokina[a], A.S. Nikolaiko[a], S. Nisi[h], R.B. Podviyanuk[a], O.G. Polischuk[a,f], A.P. Shcherban[l], V.N. Shlegel[k], D.A. Solopikhin[l], V.I. Tretyak[a], V.I. Umatov[b], Ya.V. Vasiliev[k], V.D. Virich[l]

[a] *Institute for Nuclear Research, MSP 03680 Kyiv, Ukraine*
[b] *Institute of Theoretical and Experimental Physics, 117218 Moscow, Russia*
[c] *INFN, sezione Roma "Tor Vergata", I-00133 Rome, Italy*
[d] *Dipartimento di Fisica, Università di Roma "Tor Vergata", I-00133 Rome, Italy*
[e] *Joint Institute for Nuclear Research, 141980 Dubna, Russia*
[f] *INFN, sezione Roma "La Sapienza", I-00185 Rome, Italy*
[g] *Dipartimento di Fisica, Università di Roma "La Sapienza", I-00185 Rome, Italy*
[h] *INFN, Laboratori Nazionali del Gran Sasso, I-67100 Assergi (AQ), Italy*
[i] *Kyiv National Taras Shevchenko University, MSP 03680 Kyiv, Ukraine*
[j] *Joint Stock Company NeoChem, 117647 Moscow, Russia*
[k] *Nikolaev Institute of Inorganic Chemistry, 630090 Novosibirsk, Russia*
[l] *National Science Center "Kharkiv Institute of Physics and Technology", 61108 Kharkiv, Ukraine*

Abstract

Cadmium tungstate crystal scintillators enriched in ^{106}Cd and ^{116}Cd were developed. The produced scintillators exhibit good optical and scintillation properties, and a low level of radioactive contamination. Experiments to search for double beta decay of ^{106}Cd and ^{116}Cd are in progress at the Gran Sasso National Laboratories of the INFN (Italy). Prospects to further improve the radiopurity of the detectors by recrystallization are discussed.

---

[*] Corresponding author. Tel.: +38-044-5255283; fax: +38-044-5254463.
Email address: `poda@kinr.kiev.ua` (D.V. Poda)

Preprint submitted to Radiation Measurements *February 21, 2013*

Keywords:
$CdWO_4$ crystal scintillator, Enriched isotope, ^{106}Cd, ^{116}Cd, Low counting experiment, Radiopurity, Double beta decay

1. Introduction

Two neutrino double beta ($2\nu2\beta$) decay is the rarest nuclear transformation ever observed; the half-lives are in the range of $T_{1/2} \sim 10^{18}$–10^{24} yr (see e.g. (Tretyak and Zdesenko, 1995, 2002; Barabash, 2010a)). As regards the neutrinoless mode (0ν) of the decay, a particular analysis of the data collected by the Heidelberg-Moscow collaboration, exploiting the ^{76}Ge isotope, was presented in (Klapdor-Kleingrothaus and Krivosheina, 2006); several experiments are now in progress on the same and on other isotopes to further investigate the process. Published limits on the half-life of this process in various isotopes are at level of $\lim T_{1/2} \sim 10^{23}$–$10^{25}$ yr (see e.g. (Tretyak and Zdesenko, 1995, 2002; Barabash, 2010b; Gomez-Cadenas et al., 2012)). Investigations of the $0\nu2\beta$ decay are related with several fundamental topics of particle physics: the lepton number violation, the nature of neutrino (Majorana or Dirac particle), an absolute scale of neutrino mass and the neutrino mass hierarchy (see (Rodejohann, 2011; Elliott, 2012; Vergados et al., 2012; Gomez-Cadenas et al., 2012) and references therein).

One of the most sensitive 2β experiments was realized in the Solotvina underground laboratory (Ukraine) with the help of ≈ 0.3 kg radiopure cadmium tungstate scintillators enriched in ^{116}Cd ($^{116}CdWO_4$) (Danevich et al., 2003). $CdWO_4$ crystal scintillators were also successfully used to search for 2β processes in ^{106}Cd (Danevich et al., 1996, 2003) and ^{108,114}Cd (Belli et al., 2008). The experiments showed that $CdWO_4$ scintillator is a promising detector thanks to possibility to realize calorimetric "source = detector" experiment with a high detection efficiency, low level of intrinsic radioactivity, good scintillation properties, ability of pulse-shape discrimination in order to suppress background caused by intrinsic radioactive contamination, and long operation stability. In addition, ^{116}Cd and ^{106}Cd isotopes are favorable candidates for 2β experiments thanks to the high energy of decay (≈ 2.8 MeV (Tretyak and Zdesenko, 1995, 2002)), promising theoretical estimations (e.g. see in (Tretyak and Zdesenko, 1995, 2002)), relatively large isotopic abundance (Berglund and Wieser, 2011) and possibility of enrichment by ultracentrifugation (Artyukhov et. al., 1997).

High quality ^{106}CdWO$_4$ crystal scintillator enriched in ^{106}Cd was developed for the first time (Belli et al., 2010). Large volume ^{116}CdWO$_4$ crystal was produced to investigate 2β decay of ^{116}Cd (Barabash et al., 2011). Experiments with these detectors (Belli et al., 2012; Barabash et al., 2012) demonstrate their high scintillation quality and low level of radioactive contamination. Nevertheless, taking into account that high sensitivity 2β experiments require very low, ideally zero, background, an R&D to further improve the radiopurity of the scintillators by recrystallization is in progress. Some preliminary results of this work are presented here.

2. Development and characterization of enriched ^{106,116}CdWO$_4$ scintillators

To develop crystal scintillators from enriched material, one needs to minimize loss of costly isotopically enriched materials, maximize yield of crystal scintillators, prevent radioactive contamination. Taking into account these demands, the production of the enriched ^{106}CdWO$_4$ and ^{116}CdWO$_4$ crystals has been performed in the following steps: a) purification of the isotopically enriched cadmium metal samples by means of heating with filtering and subsequent distillation through getter filter; b) chemical purification and synthesis of cadmium tungstate compounds; c) crystal growth; d) cut to produce scintillation element(s). The purity grade of all the materials was controlled at all the steps by using mass and atomic absorption spectrometry.

The purification of the enriched samples was performed by distillation through graphite filter in vacuum of 10^{-5} Torr (Bernabey et al., 2008; Kovtun et al., 2011). The procedure allowed to purify the enriched ^{106,116}Cd samples to the level of ≤ 1 ppm (Fe, Mg, Mn, Cr, V, Co), ≤ 0.2 ppm (Ni, Cu), and ≤ 0.1 ppm (Th, U, Ra, K, Rb, Bi, Pb, Lu, Sm).

After dissolving the metallic cadmium in nitric acid, the purification of cadmium nitrate was realized by the coprecipitation of the impurities on a collector. Tungsten was purified by recrystallization of ammonium para-tungstate. Solutions of cadmium nitrate and ammonium para-tungstate were mixed and then heated to precipitate cadmium tungstate:

$$\mathrm{Cd(NO_3)_2 + (NH_4)_2WO_4 \rightarrow CdWO_4 + 2NH_4NO_3}.$$

All the operations were realized by using quartz, Teflon and polypropylene labware, materials with low level of radioactive contaminations.

The boules of ^{106}CdWO$_4$ (with mass of 231 g) (Belli et al., 2010) and ^{116}CdWO$_4$ (1868 g) (Barabash et al., 2011) crystals (see Fig. 1 (a,b)) were grown in platinum crucibles by the low-thermal-gradient Czochralski technique (Pavlyuk et al., 1993). The total irrecoverable losses of the enriched cadmium on all the stages did not exceed 3%.

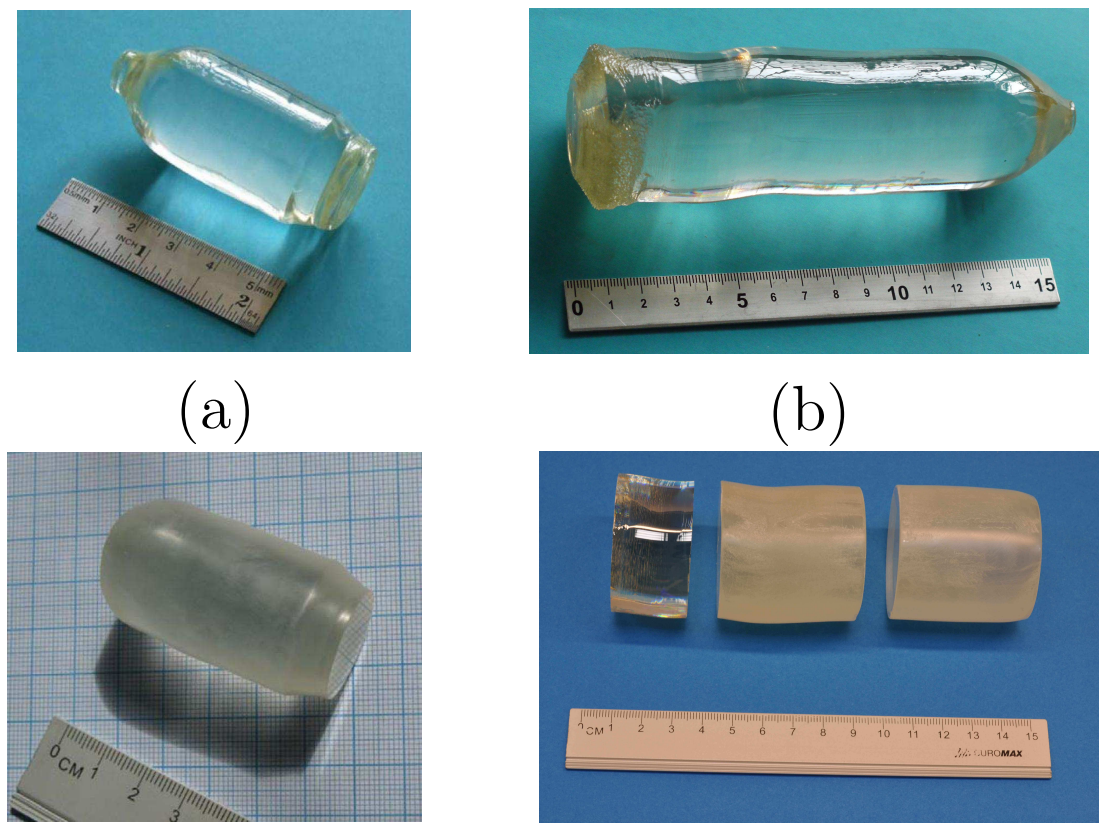

(a) (b)

(c) (d)

Figure 1: (Color online) Boules of enriched ^{106}CdWO$_4$ (a) and ^{116}CdWO$_4$ (b) crystal scintillators. The conic part of the ingots is the beginning of the crystals' growth. The scintillation element (c) produced from the ^{106}CdWO$_4$ boule: $\approx \oslash 27 \times 50$ mm, 216 g. The ^{116}CdWO$_4$ crystal samples (d) cut from the boule: $\approx \oslash 46 \times 25$ mm, 326 g (left); $\approx \oslash 45 \times 46$ mm, 582 g (middle); $\approx \oslash 45 \times 47$ mm, 580 g (right). The side surface of the ^{106,116}CdWO$_4$ scintillation elements (except of one) were diffused by using fine-grain polishing paper and diamond broach file to improve the uniformity of the scintillation light collection.

One ^{106}CdWO$_4$ scintillation element (216 g) and three ^{116}CdWO$_4$ elements (580 g, 582 g, and 326 g) were produced from the crystal ingots by cut on the cleavage plane (see Fig. 1 (c,d)). Thanks to the deep purification of starting materials and using of the low-thermal-gradient Czochralski growing method, the crystals show excellent optical and scintillation properties. For example, the attenuation length of the ^{106}CdWO$_4$ and ^{116}CdWO$_4$ scintillation elements were measured as (60 ± 7) and (31 ± 5) cm, respectively, at the wavelength of the emission maximum (490 nm).

The isotopic concentration of the isotopes of interest in the ^{106}CdWO$_4$ and ^{116}CdWO$_4$ crystals was measured by mass-spectrometry as 66.41(5)%

and 82.2(1)%, respectively[1].

The radioactive contamination of the ^{106}CdWO$_4$ crystal and of two ^{116}CdWO$_4$ samples (580 g and 582 g) was measured in scintillation mode (see Sec. 3). The radioactive contamination of the 3rd ^{116}CdWO$_4$ sample (326 g) and the scraps (264 g) after the crystal growth were checked with the help of ultra-low background γ spectrometry. All the measurements were performed deep underground at the Gran Sasso National Laboratories of the INFN (LNGS, Italy). The obtained activities (or limits) are presented in Table 1 where the data on radioactive contamination of enriched ^{116}CdWO$_4$ crystals used in the Solotvina experiment and of CdWO$_4$ scintillators produced from cadmium with the natural isotopic composition are given for comparison. The developed ^{106,116}CdWO$_4$ scintillators have low level of intrinsic radioactivity caused by the primordial ^{40}K and radionuclides from U/Th chains, anthropogenic ^{90}Sr and ^{137}Cs, cosmogenic ^{110m}Ag. We explain presence of β active ^{113m}Cd by strong neutron activation of natural cadmium samples used in the enrichment procedure.

The radioactive contamination of the scraps after the ^{116}CdWO$_4$ boule growth is much higher than that of the ^{116}CdWO$_4$ crystals. From the comparison of the data listed in Table 1, one can conclude that segregation of K, Th, and especially of Ra, by ^{116}CdWO$_4$ scintillator is very low. It gives a strong signature that the radioactive contamination of the crystals by ^{40}K, ^{228}Th and ^{226}Ra can be substantially reduced by recrystallization.

3. Double beta experiments with ^{106}CdWO$_4$ and ^{116}CdWO$_4$ scintillation detectors

Searches for double beta decays of ^{106,116}Cd were realized with the developed ^{106,116}CdWO$_4$ scintillators in the low background DAMA/R&D set-up installed at the LNGS (Italy) (Belli et al., 2012; Barabash et al., 2012).

Data were accumulated over 6590 h with the ^{106}CdWO$_4$ and during 7593 h with the ^{116}CdWO$_4$ detector. Two neutrino 2β decay of ^{116}Cd was measured with the half-life $T_{1/2} = (2.5 \pm 0.5) \times 10^{19}$ yr in agreement with the results of the previous experiments (see (Barabash et al., 2012) and references therein). Lower half-life limits were set on several possible 2β decays in the range of $\lim T_{1/2} \sim 10^{19}$–$10^{21}$ yr for ^{106}Cd (Belli et al., 2012) and $\lim T_{1/2} \sim 10^{21}$–$10^{22}$

---

[1] One can compare with isotopic abundance of ^{106}Cd and ^{116}Cd in natural Cd: 1.25(6)% and 7.49(18)%, respectively (Berglund and Wieser, 2011).

Table 1: Radioactive contamination of the enriched $^{106}\mathrm{CdWO}_4$ (Belli et al., 2012) and $^{116}\mathrm{CdWO}_4$ (Barabash et al., 2011) crystal scintillators, and of the scraps after the $^{116}\mathrm{CdWO}_4$ crystals growth. Data of Ref. (Barabash et al., 2011) have been updated. The upper limits are given at 90% C.L., and the uncertainties of the measured activities at 68% C.L. In the last two columns, data for enriched $^{116}\mathrm{CdWO}_4$ (Georgadze et al., 1996; Danevich et al., 2003) and natural CdWO_4 (Georgadze et al., 1996; Burachas et al., 1996; Danevich et al., 1996; Belli et al., 2007) are given for comparison.

Nuclide (Sub-chain)	Activity (mBq/kg)						
	$^{106}\mathrm{CdWO}_4$	$^{116}\mathrm{CdWO}_4$				$^{116}\mathrm{CdWO}_4$	CdWO_4
	216 g	580 g	582 g	326 g	scraps		
^{232}Th	≤ 0.07	≤ 0.08	≤ 0.08			0.017(5)–0.053(9)	0.015(8)–≤ 0.1
^{228}Ra				≤ 1.3	9(2)		
^{228}Th	0.042(4)	0.041(3)	0.067(4)	≤ 2.0	10(2)	0.039(2)	≤ 0.003–0.008(4)
^{235}U				≤ 4.0	≤ 14	≤ 0.007	≤ 0.005
^{227}Ac		≤ 0.002	≤ 0.002			0.0014(9)	≤ 0.005–0.014(9)
^{238}U	≤ 0.6	≤ 0.4	≤ 0.6			≤ 0.6	$\leq$(0.045–1.3)
^{234m}Pa				≤ 58	≤ 190	≤ 0.2	
^{230}Th	≤ 0.4	≤ 0.06	≤ 0.05			≤ 0.5	
^{226}Ra	0.012(3)	≤ 0.005	≤ 0.005	1.8(8)	64(4)	$\leq$(0.004–0.13)	$\leq$(0.007–0.1)
^{210}Po	≤ 0.2	≤ 0.4	≤ 0.6				≤ 0.063
Total α activity of Th/U-chains	2.1(2)	2.10(2)	2.93(2)			1.4(1)–2.8(5)	0.26(4)–≤ 0.7
^{40}K	≤ 1.4	≤ 0.9	≤ 0.9	18(8)	27(11)	0.3(1)–≤ 8.8	$\leq$(1.7–5)
^{90}Sr	≤ 0.3					$\leq$(0.2–5.6)	$\leq$(1–3)
^{110m}Ag	≤ 0.06	0.12(4)	0.12(4)				
^{113}Cd	182	100(10)	100(10)			91(5)–97	558(4)–580(20)
^{113m}Cd	$11.6(4) \times 10^3$	460(20)	460(20)			1.1(1)–30(10)	≤ 3.4–150(10)
^{137}Cs				2.1(5)	≤ 2.1	0.43(6)–1.5(4)	$\leq$(0.3–0.9)

yr for ^{116}Cd (Barabash et al., 2012), all the limits are at 90% C.L. Most of the limits are stronger than those obtained in the previous experiments.

The experiment with the ^{116}CdWO$_4$ detector is in progress. A next stage of the experiment with the enriched ^{106}CdWO$_4$ crystal in coincidence with four HPGe detectors of 225 cm^3 volume each (mounted in one cryostat) is in preparation. We estimate the sensitivity of the experiment, in particular, to $2\nu\varepsilon\beta^+$ decay of ^{106}Cd, to be at the level of theoretical predictions, $T_{1/2} \sim 10^{20}$–10^{22} yr.

4. Conclusions

Cadmium tungstate crystal scintillators have been developed from enriched cadmium isotopes: ^{106}CdWO$_4$ (231 g; 66% of ^{106}Cd) and ^{116}CdWO$_4$ (1868 g; 82% of ^{116}Cd). The total irrecoverable losses of the enriched cadmium on all the stages of scintillators production did not exceed 3%. The produced ^{106,116}CdWO$_4$ scintillators exhibit excellent optical and scintillation properties and high level of radiopurity.

The double beta experiments using ^{106,116}CdWO$_4$ scintillators are in progress at the Gran Sasso National Laboratories of the INFN (Italy). The new improved half-life limits on 2β decay of ^{106}Cd and ^{116}Cd were set on the level of $\lim T_{1/2} \sim 10^{19-21}$ yr and $\lim T_{1/2} \sim 10^{21-22}$ yr at 90% C.L., respectively. The $2\nu2\beta$ decay of ^{116}Cd was observed with the half-life $T_{1/2} = (2.5 \pm 0.5) \times 10^{19}$ yr, in agreement with results of previous experiments. The new experiment to search for 2β processes in ^{106}Cd with the ^{106}CdWO$_4$ detector placed in the GeMulti set-up with four 225 cm^3 HPGe detectors is in preparation.

We have observed very low segregation of K, Ra, and Th by cadmium tungstate crystals. It gives a strong signature of possible improvement of the crystals radiopurity by recrystallization.

References

Artyukhov, A.A., et. al., 1997. Centrifugal enrichment of cadmium isotopes as the basis for further experiments on physics of weak interactions, Nucl. Instrum. Methods Phys. Res. A 401, 281–288.

Barabash, A.S., 2010. Precise half-life values for two-neutrino double-β decay. Phys. Rev. C 81, 035501, 7 pp.

Barabash, A.S., 2010. Double-beta decay: Present status. Phys. At. Nucl. 73, 162–178.

Barabash, A.S., et al., 2011. Low background detector with enriched ^{116}CdWO$_4$ crystal scintillators to search for double β decay of ^{116}Cd. J. Instrum. 6, P08011, 24 pp.

Barabash, A.S., et al., 2012. First results of the experiment to search for double beta decay of ^{116}Cd with the help of enriched ^{116}CdWO$_4$ crystal. To be published in: Proceedings of the 4th International Conference "Current Problems in Nuclear Physics and Atomic Energy" (NPAE-2012), 03–07 September 2012, Kyiv, Ukraine.

Belli, P., et al., 2007. Investigation of beta decay of ^{113}Cd. Phys. Rev. C 76, 064603, 10 pp.

Belli, P., et al., 2008. Search for double-β decay processes in ^{108}Cd and ^{114}Cd with the help of the low background CdWO$_4$ crystal scintillator. Eur. Phys. J. A 36, 167–170.

Belli, P., et al., 2010. Development of enriched ^{106}CdWO$_4$ crystal scintillators to search for double β decay processes in ^{106}Cd, Nucl. Instrum. Methods Phys. Res. A 615, 301–306.

Belli, P., et al., 2012. Search for double-β decay processes in ^{106}Cd with the help of a ^{106}CdWO$_4$ crystal scintillator. Phys. Rev. C 85, 044610, 10 pp.

Berglund, M., and Wieser, M.E., 2011. Isotopic compositions of the elements 2009 (IUPAC technical report). Pure Appl. Chem. 83, 397–410.

Bernabey, R., et al., 2008. Production of high purity Cd and ^{106}Cd for CdWO$_4$ and ^{106}CdWO$_4$ scintillators [in Russian]. Metallofiz. Nov. Tekhnol. 30, 477–486.

Burachas, S.Ph., et al., 1996. Large volume CdWO$_4$ crystal scintillators. Nucl. Instrum. Methods Phys. Res. A 369, 164–168.

Danevich, F.A., et al., 1996. Investigation of $\beta^+\beta^+$ and β^+/EC decay of ^{106}Cd. Z. Phys. A 355, 433–437.

Danevich, F.A., et al., 2003. Search for 2β decay of cadmium and tungsten isotopes: final results of the Solotvina experiment. Phys. Rev. C 68, 035501, 12 pp.

Elliott, S.R., 2012. Recent progress in double beta decay. Mod. Phys. Lett. A 27, 1230009, 16 pp.

Georgadze, A.Sh., et al., 1996. Evaluation of activities of impurity radionuclides in cadmium tungstate crystals. Instrum. Exp. Tech. 39, 191–198 [Translated from Prib. Tekh. Exp. 2 (1996) 45–51].

Gomez-Cadenas, J.J., Martin-Albo, J., Mezzetto, M., Monrabal, F., Sorel, M., 2012. The search for neutrinoless double beta decay. Riv. Nuovo Cimento 35, 29–98.

Klapdor-Kleingrothaus, H.V., Krivosheina, I.V, 2006. The evidence for the observation of $0\nu\beta\beta$ decay: The identification of $0\nu\beta\beta$ events from the full spectra. Mod. Phys. Lett. A 21, 1547–1566.

Kovtun, G.P., et al., 2011. Production of radiopure natural and isotopically enriched cadmium and zinc for low background scintillators. Functional Materials 18, 121–127.

Pavlyuk, A.A., et al., 1993. Low Thermal Gradient technique and method for large oxide crystals growth from melt and flux. In: Proceedings of the APSAM-92 meeting (Asia Pacific Society for Advanced Materials), 26–29 April 1992, Shanghai, China; Institute of Materials Research, Tohoku University, Sendai, Japan, p. 164.

Rodejohann, W., 2011. Neutrino-less double beta decay and particle physics. Int. J. Mod. Phys. E 20, 1833–1930.

Tretyak, V.I., and Zdesenko, Yu.G., 1995. Tables of double beta decay data. At. Data Nucl. Data Tables 61, 43–90.

Tretyak, V.I., and Zdesenko, Yu.G., 2002. Tables of double beta decay data — an update. At. Data Nucl. Data Tables 80, 83–116.

Vergados, J.D., Ejiri, H., and Ŝimkovic, F., 2012. Theory of neutrinoless double-beta decay. Rep. Prog. Phys. 75, 106301, 52 pp.